

AD-A105 556

ATLANTA UNIV GA DEPT OF CHEMISTRY

F/S 11/9

LIQUID CRYSTAL BLOCK COPOLYESTERS. II. PREPARATION AND PROPERTIES-ETC(U)

SEP 81 M B POLK; K B BOTA; E C AKUBUIRO

N00014-80-C-0557

UNCLASSIFIED

NL

1 OF 1
AD A
105 556

END
DATE
FILMED
11-81
DTIC

AD A105556

DTIC FILE COPY

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 1	2. GOVT ACCESSION NO. AD-A105556	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Liquid Crystal Block Copolyesters. II. Preparation and Properties of Block Copolyesters Containing Cyclohexane and Benzene Rings.		5. TYPE OF REPORT & PERIOD COVERED Technical Report, 1/1/80. 5/31/81
7. AUTHOR(s) Malcolm B. Polk, Kofi B. Bota, Edmond C. Akubuiro and Metha Phingbodhipakkiya		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Malcolm B. Polk Chemistry Department Atlanta University; Atlanta, Georgia 30314		8. CONTRACT OR GRANT NUMBER(s) N00014-80-C-0557
11. CONTROLLING OFFICE NAME AND ADDRESS Department of the Navy Office of Naval Research-Chemistry Arlington, VA 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 356-745
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) LEVEL II		12. REPORT DATE September 28, 1981
		13. NUMBER OF PAGES 22
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) This document has been approved for public release. Distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES To be published in <u>Macromolecules</u> .		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Polymers Polymerization Block Copolymers Liquid crystalline polymers Lyotropic		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Poly [oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] V; Poly[oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl] VI; Poly[oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl] VII; and Poly[oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] VIII		

DD FORM 1473

JAN 73

EDITION OF 1 NOV 65 IS OBSOLETE

S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

295277

Report Documentation Page 2, paragraph 20 continued (Abstract)

have been synthesized and characterized by infrared spectroscopy, nuclear magnetic resonance spectroscopy, differential scanning calorimetry, and viscometry. Block copolymers VI, VII and VIII form mesomorphic solutions which depolarize plane-polarized light.

Accession For	
NTIS GRA&I	<input checked="checked" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist	Special
A	

OFFICE OF NAVAL RESEARCH

Contract N00014-80-C-0557

Task No. NR 356-745

TECHNICAL REPORT NO. 1

Liquid Crystal Block Copolyesters. II. Preparation
and Properties of Block Copolyesters Containing
Cyclohexane and Benzene Rings

by

Malcolm B. Polk, Kofi B. Bota, Edmond C. Akubuiro
and Metha Phingbodhipakkiya

Prepared for Publication

in

Macromolecules

Atlanta University
Department of Chemistry
Atlanta, Georgia

September 28, 1981

Reproduction in whole or in part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

81 10 5 158

Liquid Crystal Block Copolyesters. II. Preparation and Properties of Block Copolyesters Containing Cyclohexane and Benzene Rings.

Malcolm B. Polk, Kofi B. Bota, Edmond C. Akubuiro and Metha Phingbodhipakkiya

Department of Chemistry, Atlanta University, Atlanta, Georgia 30314

ABSTRACT. Poly[oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] V; Poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl)VI; Poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl -b -oxy-1,4-phenyleneoxyterephthaloyl)VII; and Poly[oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] VIII have been synthesized and characterized by infrared spectroscopy, nuclear magnetic resonance spectroscopy, differential scanning calorimetry, and viscometry. Block copolymers VI, VII and VIII form mesomorphic solutions which depolarize plane-polarized light.

Introduction

This is the second in a series of papers which describe the synthesis and characterization of a number of block copolyesters which contain cyclohexane and benzene rings. A number of these block copolyesters in solution have been shown to rotate the plane of cross-polarized light and therefore may be said to form liquid crystalline solutions.

The first paper in the series described the syntheses and characterizations of the following block copolyesters: I. poly(oxy-cis,trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl); II. poly[oxy-cis,trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl]; III. poly[oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyisophthaloyl]; and IV. poly[oxy-cis-1,2-cyclohexyleneoxycarbonyl-cis-1,2-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyisophthaloyl].¹ Poly[oxy-cis,trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] was shown to form mesomorphic solutions which depolarize plane-polarized light.

Kuhfuss and coworkers² have prepared random copolyesters by the acidolysis of poly(ethylene terephthalate) with p-acetoxybenzoic acid. They found that copolyesters which contained 40-90 mole percent para oxybenzoyl groups formed liquid crystalline melts. McFarlane and coworkers³ have reported that replacement of para oxybenzoyl groups with meta oxybenzoyl groups and 1,3-oxyphenyleneoxyterephthaloyl groups in the random copolyesters reduces the chain linearity to such an extent that liquid crystalline behavior disappears. While studying the properties of block copolyesters, which form liquid crystalline mesophases, we have observed a greater tolerance of the rod-like, extended chain blocks for nonconforming blocks containing groups such as oxy(2-methyl-1,3-phenylene)oxyterephthaloyl.^{1,4}

Several problems have been encountered in attempts to process these liquid crystalline polymers: (1) the relative insolubility of the polymers in organic solvents; (2) the decomposition of the polymers at the high temperatures required for processing; and (3) the low elongations-to-break of the fibers which decrease after exposure to a high temperature.

Our purpose in initiating these research efforts was to prepare liquid crystalline materials with increased solubility, lower processing temperatures, and higher levels of thermal stability. We set out to achieve these goals in a somewhat different fashion than that of other researchers in the field.⁵⁻²³ We decided to optimize the solubility, thermal, and mechanical properties of block copolyesters which contain cyclohexane and benzene rings by incorporating blocks which contained nonconforming groups into (AB)_n block copolyesters which also contained extended chain blocks.

Experimental Section

Inherent viscosities were measured at 30°C with a Cannon-Fenske viscometer at a concentration of 0.5 g/100 mL solvent except in those cases specified. Melting points and glass transition temperatures were determined with a differential scanning calorimeter (DuPont 990 and 1090 thermal analyzers with the DuPont 910 differential scanning calorimeter). NMR spectra were determined on deuteriochloroform solutions of the polyesters with a Bruker WH-250 spectrometer with proton at 250.133 MHz and carbon-13 at 62.860 MHz. The chemical shifts are reported relative to tetramethylsilane. Infrared spectra were obtained on KBr discs with a Beckman 4240 infrared spectrophotometer. Polarizing microscopy was performed on an Aus Jena Amplival Pol. D polarizing microscope. Elemental analysis was provided by Galbraith Laboratories. Terephthaloyl chloride, trans-1,2-cyclohexanediol, cis-1,4-cyclohexanediol, hydroquinone and methylhydroquinone were commercial products. Trans-1,4-cyclohexanedicarboxylic acid chloride and trans-1,2-cyclohexanedicarboxylic acid chloride were prepared according to a procedure described in the literature.²⁴ Trans-1,4-cyclohexanediol was isolated from the cis,trans-1,4-cyclohexanediol mixture according to a procedure described in the literature.²⁵

The o-dichlorobenzene solvent used in the polyesterification was purified and dried by fractional distillation and stored over molecular sieves. Trans-1,4-cyclohexanedicarboxylic acid chloride and trans-1,2-cyclohexanedicarboxylic acid chloride were purified by distillation. Terephthaloyl chloride was purified by recrystallization from dry hexane. Hydroquinone and methylhydroquinone were purified by recrystallization from deoxygenated water.

A. Preparation of poly [oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] V.

A 500 mL three-necked, round-bottom flask, equipped with a magnetic stirrer, a condenser, a nitrogen inlet, a thermometer, and a potassium hydroxide trap was charged with 25.74 g (0.2220 mole) of trans-1,2-cyclohexanediol and 120 mL of dry o-dichlorobenzene. To the stirred solution was added 42.08 g (0.2000 mole) of trans-1,2-cyclohexanedicarboxylic acid chloride in an atmosphere of nitrogen. The mixture was heated for 1-1/4 hr at 115°C, accompanied by the evolution of HCl. The mixture was then heated under reflux for 7-1/2 hr.

A 500 mL three-necked, round-bottom flask, equipped with a magnetic stirrer, a condenser, a nitrogen inlet, a thermometer, and a potassium hydroxide trap was charged with 25.0 g (0.200 mole) of 2-methylresorcinol and 180 mL of dry o-dichlorobenzene. To this stirred solution was added 46.0 g (0.2266 mole) of terephthaloyl chloride in an atmosphere of nitrogen. The mixture was heated for 1 hr. at 120°C. The mixture was then heated under reflux for 6-1/2 hr.

After cooling, 60 ml of each of the two polyester solutions were mixed thoroughly in an atmosphere of nitrogen and heated under reflux for 1-1/2 hrs. The mixture was then heated for 8 hrs. at 150°C. After cooling, the polymer was

precipitated by pouring the reaction mixture into 500 mL of hexane. The polymer was allowed to stand in hexane for 1 day. After washing twice with acetone, three times with deionized water, and finally with acetone, 11 g of polymer was obtained after drying in a vacuum oven for 48 hrs. at 120°C.

B. Preparation of poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl)VI.

The same procedure in A was followed. For the preparation of the cycloaliphatic oligomer, 28.70 g (0.1373 mole) of trans-1,4-cyclohexanedicarboxylic acid chloride, 17.56 g (0.1510 mole) of trans-1,4-cyclohexanediol, and 190 mL of dry o-dichlorobenzene were used. For the preparation of the aromatic oligomer, 44.70 g (0.2200 mole) of terephthaloyl chloride, 22.02 g (0.2000 mole) of hydroquinone, and 240 mL of dry o-dichlorobenzene were used. After 100 mL of each solution were mixed, refluxed and heated, 17 g of VI were obtained by precipitation with acetone.

C. Preparation of poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl)VII.

The same procedure in A was followed. For the preparation of the cycloaliphatic oligomer, 10.4 g (0.0894 mole) of cis-1,4-cyclohexanediol, 17.0 g (0.0813 mole) of trans-1,4-cyclohexanedicarboxylic acid chloride, and 110 mL of dry o-dichlorobenzene were used. For the preparation of the aromatic oligomer 11.0 g (0.100 mole) of hydroquinone, 22.4 g (0.110 mole) of terephthaloyl chloride, and 120 mL of dry o-dichlorobenzene were used. After 50 mL of each solution were mixed, refluxed and heated, 18 g of VII were obtained by precipitation with acetone.

D. Preparation of poly [oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] VIII.

The same procedure in A was followed. For the preparation of the cycloaliphatic oligomer, 25.5 g (0.220 mole) of trans-1,4-cyclohexanediol, 41.8 g (0.200 mole) of trans-1,4-cyclohexanedicarboxylic acid chloride, and 300 mL of dry o-dichlorobenzene were used. For the preparation of the aromatic oligomer, 24.8 g (0.200 mole) of methylhydroquinone, 44.7 g (0.220 mole) of terephthaloyl chloride, and 300 mL of dry o-dichlorobenzene were used. After 150 mL of each solution were mixed, refluxed and heated, 50 g of XIII were obtained by precipitation with acetone.

Results and Discussion

Four block copolyesters were formed by the step-reaction condensation of cycloaliphatic ester oligomers capped with dihydroxy end groups and aromatic ester oligomers capped with dicarboxylic acid chloride end groups (see Scheme 1). The structures of the resulting block copolyesters are shown in Figure 1.

Properties of Poly [oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylene-carbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] V.

The inherent viscosities for poly(oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl) and poly[oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] were 0.06 and 0.44 dL/g, respectively at 30°C in m-cresol. The inherent viscosity of the corresponding block copolyester, poly[oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl-b-oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] was 0.27 dL/g at 30°C in m-cresol.

Elemental analysis showed a number average degree of polymerization of five for the poly(oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl) oligomer. Anal. Calcd for $\text{H}-(\text{C}_{14}\text{H}_{20}\text{O}_4)_5-\text{C}_6\text{H}_{11}\text{O}_2\cdot 2\text{H}_2\text{O}$: C, 64.59; H, 8.22. Found: C, 64.22; H, 8.13. Elemental analysis showed a number average degree of polymerization of seventeen for the poly[(2-methyl-1,3-phenylene)oxyterephthaloyl] oligomer. Anal. Calcd for $\text{HO}-(\text{C}_{15}\text{H}_{10}\text{O}_4)_{17}-\text{C}_8\text{H}_5\text{O}_3$: C, 70.38; H, 3.93. Found: C, 70.20; H, 4.18.

The infrared spectrum showed peaks at 3400 (O-H stretch), 2910 and 2840 (aliphatic C-H stretch), 1720 (ester C=O stretch), 1450 (aromatic nucleus), and 1250, 1070, and 1005 (C-O stretch) cm^{-1} .

The differential scanning calorimetry thermogram of poly(oxy-trans-1,2-cyclohexyleneoxycarbonyl-trans-1,2-cyclohexylenecarbonyl) showed a glass transition temperature of 68°C . The differential scanning calorimetry thermogram of poly[oxy(2-methyl-1,3-phenylene)oxyterephthaloyl] showed a crystalline melting point of 313°C . The differential scanning calorimetry thermogram of the corresponding block copolyester showed a melting endotherm at 320°C .

The ^1H NMR spectrum of the block copolymer was obtained in CDCl_3 . The ^1H chemical shifts and integrals were as follows: δ 1.26 (1.0), 1.32 (3.1), 1.74 (3.1), 1.82 (0.2), 1.85 (0.7), 1.99 (1.9), 2.15 (1.8), 2.56 (0.8), 3.74 (0.4), 4.79 (1.1), 7.20 (0.3), 7.34 (0.2), 7.36 (0.2), 8.25 (0.3), and 8.38 (1.3) ppm. The resonances at δ 1.26 - 4.79 ppm represent aliphatic protons, and the resonances at δ 7.20 - 8.38 ppm represent aromatic protons.

Properties of Poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylene-carbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl) VI.

The inherent viscosity of poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-

cyclohexylenecarbonyl) was 0.31 dL/g in *o*-chlorophenol at 30°C. Poly(oxy-1,4-phenyleneoxyterephthaloyl) was insoluble in *o*-chlorophenol. An inherent viscosity of 0.43 dL/g was obtained for poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl) at a concentration of 0.4 g/100 mL *o*-chlorophenol at 30°C.

Elemental analysis showed a number average degree of polymerization of sixteen for the poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl) oligomer. Anal. Calcd for $\text{H}-(\text{C}_{14}\text{H}_{20}\text{O}_4)_{16}-\text{C}_6\text{H}_{11}\text{O}_2\cdot\text{H}_2\text{O}$: C, 66.26; H, 8.02. Found: C, 66.16; H, 8.24. Elemental analysis showed a number average degree of polymerization of 12 for the poly(oxy-1,4-phenyleneoxyterephthaloyl) oligomer. Anal. Calcd for $\text{HO}-(\text{C}_{14}\text{H}_8\text{O}_4)_{12}-\text{C}_8\text{H}_5\text{O}_3\cdot\text{H}_2\text{O}$: C, 68.92; H, 3.39. Found: C, 68.72, H, 3.66.

The infrared spectrum of the block copolyester showed peaks at 3400 (O-H stretch), 2930 and 2850 (aliphatic C-H stretch), 1715 (ester C=O stretch), 1600 and 1490 (aromatic nucleus) and 1240, 1070, 1035 and 1010 (C-O stretch) cm^{-1} .

The ^1H NMR spectrum of the block copolyester was obtained in CDCl_3 . The ^1H chemical shifts and integrals are as follows: δ 1.26 (1), 1.51 (15), 1.65 (1), 1.72 (1), 1.84 (3), 1.91 (1), 1.95 (1), 2.05 (4), 3.73 (3), 8.09 (1) and 8.11 (1) ppm. The resonances at δ 1.26 - 3.73 ppm represent aliphatic protons and the resonances at δ 8.09 and 8.11 ppm represent aromatic protons.

Methylene chloride - *o*-chlorophenol solutions of poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl) depolarized plane-polarized light when thin layers of the solutions were viewed at 504 X magnification.

Properties of Poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl)VII.

The inherent viscosity of poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl) was 0.18 dL/g in m-cresol at 30°C. Poly(oxy-1,4-phenyleneoxyterephthaloyl) was insoluble in m-cresol. An inherent viscosity of 0.44 dL/g was obtained for poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl) at a concentration of 0.4 g/100 mL m-cresol at 30°C.

The infrared spectrum of the block copolyester showed peaks at 3400 (O-H stretch), 2940 and 2860 (aliphatic C-H stretch), 1720 (ester C=O stretch), 1495 (aromatic nucleus), and 1245, 1070, 1035 and 1010 (C-O stretch) cm^{-1} .

The differential scanning calorimetry thermogram of poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl) showed a crystalline melting point of 220°C. The transitions in the block copolyester were obscured by decomposition.

The ^1H NMR spectrum of the block copolymer was obtained in CDCl_3 . The ^1H chemical shifts and integrals were as follows: δ 1.26 (1.1), 1.41 (3.4), 1.46 (9.5), 1.49 (3.9), 1.54 (6.6), 1.73 (16.1), 1.91 (5.4), 1.95 (3.0), 2.06 (16.8), 2.27 (7.3), 3.95 (0.3), 4.84 (7.2), 5.13 (0.7), 7.32 (0.2), 8.08 (0.3), 8.11 (0.3), 8.12 (0.1), 8.14 (0.6) and 8.20 (0.2) ppm. The resonances at δ 1.26 - 5.13 ppm represent aliphatic protons and the resonances at δ 7.32 - 8.20 ppm represent aromatic protons.

Methylene chloride - o-chlorophenol solutions of poly(oxy-cis-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy-1,4-phenyleneoxyterephthaloyl) depolarized plane-polarized light when thin layers of the solutions were viewed at 504 X magnification.

Properties of Poly[oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylene-carbonyl-b-oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] VIII.

The inherent viscosities of poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl) and poly[oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] were 0.55 and 0.58 dL/g, respectively, in 3:1 v/v methylene chloride - trifluoroacetic acid at 30°C. The inherent viscosity for the corresponding block copolyester was 0.85 dL/g in 3:1 v/v methylene chloride - trifluoroacetic acid at 30°C.

Elemental analysis showed a number average degree of polymerization of twenty for the poly(oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl) oligomer. Anal. Calcd for $\text{H}-(\text{C}_{14}\text{H}_{20}\text{O}_4)_{20}-\text{C}_6\text{H}_{11}\text{O}_2$: C, 66.56; H, 7.99. Found: C, 66.38; H, 8.36. Elemental analysis showed a number average degree of polymerization of ten for the poly[oxy(2-methyl-1,4-phenylene)oxyterephthaloyl] oligomer. Anal. Calcd. for $\text{HO}-(\text{C}_{15}\text{H}_{10}\text{O}_4)_{10}-\text{C}_8\text{H}_5\text{O}_3\cdot\text{H}_2\text{O}$: C, 69.60; H, 3.96. Found: C, 69.82; H, 4.35.

The infrared spectrum showed peaks at 2940 (aliphatic C-H stretch), 1740 (ester C=O stretch), 1410 (aromatic C-H deformation), and 1250 and 1080 (C-O stretch) cm^{-1} .

The ^1H NMR spectrum of the block copolyester was obtained in CDCl_3 . The ^1H chemical shifts and integrals were as follows: δ 1.26 (3), 1.66 (2), 1.85 (4), 2.03 (1), 2.07 (3), 2.20 (2), 2.29 (3), 2.30 (2), 4.9 (1), 5.22 (2), 6.95 (1), 7.02 (1), 7.22 (1), 7.29 (1), 8.13 (1), 8.18 (1), 8.22 (1), 8.33 (1), 8.35 (1), 8.37 (1), and 8.39 (3). The resonances at δ 1.26 - 5.22 ppm represent aliphatic protons and the resonances at δ 6.95 - 8.39 ppm represent aromatic protons.

The proton-decoupled natural abundance ^{13}C FT NMR spectrum of the block copolyester was obtained in CDCl_3 . The ^{13}C chemical shifts (relative to TMS) and integrals were as follows: 21.5 (0.2), 27.9 (0.3), 28.2 (0.2), and 130.5 (0.4) ppm. The resonances at 21.5 - 28.2 ppm represent aliphatic carbons. The resonance at 130.5 ppm

represents aromatic carbons. The resonances due to the carbonyl carbons were not observed due to the limited solubility of the block copolyester.

1,1,2,2-Tetrachloroethane-o-chlorophenol-phenol (60:25:15 v/v/v) solutions of poly oxy-trans-1,4-cyclohexyleneoxycarbonyl-trans-1,4-cyclohexylenecarbonyl-b-oxy(2-methyl-1,4-phenylene)oxyterephthaloyl depolarized plane-polarized light when thin layers of the solutions were viewed at 100 X magnification. When the solutions were sheared by the movement of the cover slide, microdomains of oriented, extended chain segments were observed to form on microscopic examination between crossed polarizers. This phenomenon is shown in Figure 2.

Conclusion

In summary, synthetic procedures have been developed for block copolyesters which contain cyclohexane and benzene rings. Three of these block copolyesters display mesomorphic properties in solution. In subsequent publications, the spectroscopic, mechanical, and thermal properties of these block copolyesters will be described in detail.

Acknowledgements. The authors would like to acknowledge Dr. Yitbarek H. Mariam and Mr. William Lewis for obtaining NMR data. Support from the Office of Naval Research under grant number N00014-80-C-0577 and the Resource Center for Science and Engineering at Atlanta University funded by the National Science Foundation under grant number 78-11955 is also acknowledged.

References and Notes

1. M. B. Polk, K. B. Bota, and E. C. Akubuiro, submitted to I & EC Product R/D.
2. W. J. Jackson and H. F. Kuhfuss, J. Polym. Sci., **14**, 2043 (1976).

3. F. E. McFarlane, V. A. Nicely, and T. G. Davis in "Polyesters Exhibiting Liquid Crystal Melts", E. M. Pearce and J. R. Schaefgen, Contemporary Topics in Polymer Science, Vol. 2, Plenum Press, New York, 1977, p. 115-120.
4. M. B. Polk, K. B. Bota, and E. C. Akubuiro, Prepr. Div. Org. Coat. Plast. Am. Chem. Soc., 44, 416 (1981).
5. J. R. Schaefgen, T. C. Pletcher, and J. J. Kleinschuster, Belgium Patent 828,935 (1975).
6. T. C. Pletcher, U. S. Patent 3,991,013, (1976).
7. J. J. Kleinschuster, U. S. Patent 3,991,014 (1976).
8. J. J. Kleinschuster and T. C. Pletcher, U. S. Patent 4,066,620 (1978).
9. G. W. Calundann, U. S. Patent 4,067,852 (1978).
10. J. R. Schaefgen, U. S. Patent 4,075,262 (1978).
11. G. W. Calundann, H. L. Davis, F. J. Gorman, and R. M. Mininni, U. S. Patent 4,083,329 (1978).
12. J. R. Schaefgen, U. S. Patent 4,118,372 (1978).
13. G. W. Calundann, U. S. Patent 4,130,545 (1978).
14. W. J. Jackson, Jr. and H. F. Kuhfuss, U. S. Patent 4,140,846 (1979).
15. J. C. Morris and W. J. Jackson, U. S. Patent 4,146,702 (1979).
16. W. J. Jackson, Jr., G. G. Bebeau, and H. F. Kuhfuss, U. S. Patent 4,153,779 (1979).
17. W. J. Jackson, Jr. and J. C. Morris, U. S. Patent 4,156,070 (1979).

18. G. W. Calundann, U. S. Patent 4,161,470 (1979).
19. W. J. Jackson, Jr. and J. C. Morris, U. S. Patent 4,169,933 (1979).
20. W. J. Jackson, Jr. and J. C. Morris, U. S. Patent 4,181,792 (1980).
21. G. W. Calundann, U. S. Patent 4,184,996 (1980).
22. H. Blades, U. S. Patent 3,767,756 (1973).
23. A. H. Frazer, U. S. Patent 3,037,960 (1962).
24. W. E. Doering, M. Farber, and A. Sayigh, J. Am. Chem. Soc., 74, 4370-2 (1952).
25. R. C. Oberg, H. Pines, and V. N. Ipatieff, J. Am. Chem. Soc., 66, 1096-9 (1944).

SYNTHESIS OF BLOCK COPOLYESTERS

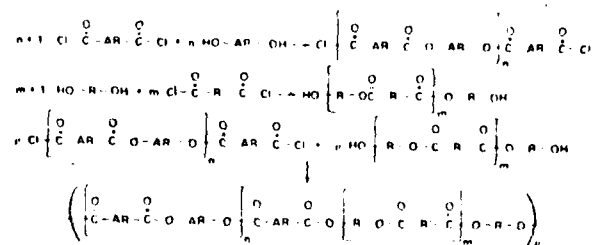


FIGURE 1
BLOCK COPOLYMERS

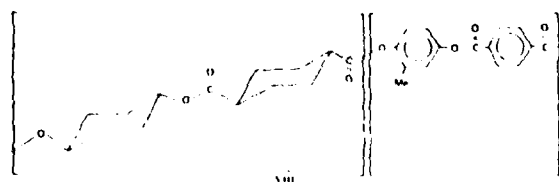
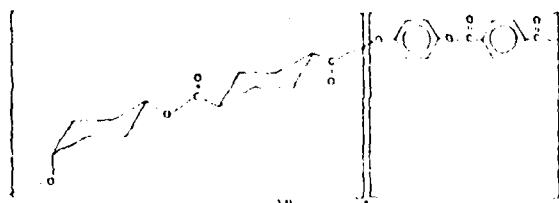
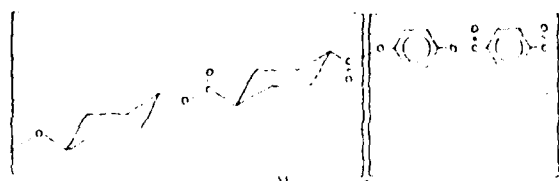





Figure 2. Micrograph of Block Copolyester VII Between Crossed Polarizers. 100X Magnification.

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Office of Naval Research Attn: Code 472 800 North Quincy Street Arlington, Virginia 22217	2	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 1211 Research Triangle Park, N.C. 27709	1
ONR Branch Office Attn: Dr. George Sandoz 536 S. Clark Street Chicago, Illinois 60605	1	Naval Ocean Systems Center Attn: Mr. Joe McCartney San Diego, California 92152	1
ONR Area Office Attn: Scientific Dept. 715 Broadway New York, New York 10003	1	Naval Weapons Center Attn: Dr. A. B. Amster, Chemistry Division China Lake, California 93555	1
ONR Western Regional Office 1030 East Green Street Pasadena, California 91106	1	Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko Port Hueneme, California 93401	1
ONR Eastern/Central Regional Office Attn: Dr. L. H. Peebles Building 114, Section D 666 Summer Street Boston, Massachusetts 02210	1	Department of Physics & Chemistry Naval Postgraduate School Monterey, California 93940	1
Director, Naval Research Laboratory Attn: Code 6100 Washington, D.C. 20390	1	Dr. A. L. Slafkosky Scientific Advisor Commandant of the Marine Corps (Code RD-1) Washington, D.C. 20380	1
The Assistant Secretary of the Navy (RE&S) Department of the Navy Room 4E736, Pentagon Washington, D.C. 20350	1	Office of Naval Research Attn: Dr. Richard S. Miller 800 N. Quincy Street Arlington, Virginia 22217	1
Commander, Naval Air Systems Command Attn: Code 310C (H. Rosenwasser) Department of the Navy Washington, D.C. 20360	1	Naval Ship Research and Development Center Attn: Dr. G. Bosmajian, Applied Chemistry Division Annapolis, Maryland 21401	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12	Naval Ocean Systems Center Attn: Dr. S. Yamamoto, Marine Sciences Division San Diego, California 91232	1
Dr. Fred Saalfeld Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1

TECHNICAL REPORT DISTRIBUTION LIST, GEN

No.
Copies

Dr. Rudolph J. Marcus
Office of Naval Research
Scientific Liaison Group
American Embassy
APO San Francisco 96503

1

Mr. James Kelley
DTNSRDC Code 2803
Annapolis, Maryland 21402

1

TECHNICAL REPORT DISTRIBUTION LIST, 356B

	<u>No.</u> <u>Copies</u>		<u>No.</u> <u>Copies</u>
Dr. T. C. Williams Union Carbide Corporation Chemical and Plastics Tarrytown Technical Center Tarrytown, New York	1	Douglas Aircraft Company Attn: Technical Library C1 290/36-84 AUTO-Sutton 3855 Lakewood Boulevard Long Beach, California 90846	1
Dr. R. Soulen Contract Research Department Pennwalt Corporation 900 First Avenue King of Prussia, Pennsylvania 19406	1	NASA-Lewis Research Center Attn: Dr. T. T. Serafini, MS 49-1 21000 Brookpark Road Cleveland, Ohio 44135	1
Dr. A. G. MacDiarmid University of Pennsylvania Department of Chemistry Philadelphia, Pennsylvania 19174	1	Dr. J. Griffith Naval Research Laboratory Chemistry Section, Code 6120 Washington, D.C. 20375	1
Dr. C. Pittman University of Alabama Department of Chemistry University, Alabama 35486	1	Dr. G. Goodman Globe-Union Incorporated 5757 North Green Bay Avenue Milwaukee, Wisconsin 53201	1
Dr. H. Allcock Pennsylvania State University Department of Chemistry University Park, Pennsylvania 16802	1	Dr. E. Fischer, Code 2853 Naval Ship Research and Development Center Annapolis Division Annapolis, Maryland 21402	1
Dr. M. Kenney Case-Western University Department of Chemistry Cleveland, Ohio 44106	1	Dr. Martin H. Kaufman, Head Materials Research Branch (Code 4542) Naval Weapons Center China Lake, California 93555	1
Dr. R. Lenz University of Massachusetts Department of Chemistry Amherst, Massachusetts 01002	1	Dr. J. Magill University of Pittsburg Metallurgical and Materials Engineering Pittsburg, Pennsylvania 22230	1
Dr. M. David Curtis University of Michigan Department of Chemistry Ann Arbor, Michigan 48105	1	Dr. C. Allen University of Vermont Department of Chemistry Burlington, Vermont 05401	1
Dr. M. Good Division of Engineering Research Louisiana State University Baton Rouge, Louisiana 70803	1	Dr. D. Bergbreiter Texas A&M University Department of Chemistry College Station, Texas 77843	1

TECHNICAL REPORT DISTRIBUTION LIST, 356BNo.
Copies

Professor R. Drago
Department of Chemistry
University of Illinois
Urbana, Illinois 61801 1

Dr. F. Brinkman
Chemical Stability & Corrosion
Division
Department of Commerce
National Bureau of Standards
Washington, D.C. 20234 1

Professor H. A. Titus
Department of Electrical Engineering
Naval Postgraduate School
Monterey, California 93940 1

COL R. W. Bowles, Code 100M
Office of Naval Research
800 N. Quincy Street
Arlington, Virginia 22217 1

Professor T. Katz
Department of Chemistry
Columbia University
New York, New York 10027 1

Professor James Chien
Department of Chemistry
University of Massachusetts
Amherst, Massachusetts 01002 1

~~Professor Malcolm B. Park~~
~~Department of Chemistry~~
~~Atlanta University~~
~~Atlanta, Georgia 30314~~ 1